

# 13 Synthesis of Matrix Si-K-HAs Gel from Geothermal Sludge and Peat

*By* Srie Muljani

See discussions, stats, and author profiles for this publication at: <https://www.researchgate.net/publication/326197425>

## Synthesis of Matrix Si-K-HAs Gel from Geothermal Sludge and Peat

Article · August 2018

DOI: 10.14710/iahe.v13i2.2949

CITATION

1

READS

25

4 authors, including:



Sri Mulyani

University of Pembangunan Nasional Veteran Jawa Timur

10 PUBLICATIONS 10 CITATIONS

[SEE PROFILE](#)

Some of the authors of this publication are also working on these related projects:



Composite of silica-humic acid [View project](#)



geothermal sludge [View project](#)

## Synthesis of Matrix Si-K-HAs Gel from Geothermal Sludge and Peat

Srie Muljani<sup>1,2,\*</sup>, Bambang Wahyudi<sup>2</sup>, Suprihatin<sup>2</sup>, and Ketut Sumada<sup>3</sup>

<sup>1</sup>Department of Chemical Engineering, Faculty of Engineering,  
University of Pembangunan Nasional Veteran Jawa Timur  
Jl. Raya Rungkut Madya Gunung Anyar Surabaya  
Telp./Fax: (031) 8706372 / (031)8706369

<sup>2</sup>Advanced Material Laboratory, University of Pembangunan Nasional Veteran Jawa Timur  
Jl. Raya Rungkut Madya Gunung Anyar Surabaya  
Telp./Fax: (031) 8706372 / (031)8706369

<sup>3</sup>Waste Treatment Laboratory, University of Pembangunan Nasional Veteran Jawa Timur  
Jl. Raya Rungkut Madya Gunung Anyar Surabaya  
Telp./Fax: (031) 8706372 / (031)8706369

\*Corresponding author: [sriemuljani.tk@upnjatim.ac.id](mailto:sriemuljani.tk@upnjatim.ac.id)

(Received: April 21, 2018; Accepted: June 04, 2018)

### Abstract

The synthesis of matrix silica-potassium-humic acid gel (Si-K-HAs) has been performed successfully by gradual extraction and acidification method. The extraction was carried out in two stages: 1) extraction of humic substances from peat prepared by potassium hydroxide to produce potassium humate (K-HAs) solution, 2) extraction silica from geothermal sludge using K-HAs solution to produce Si-K-HAs solution. Acidification of Si-K-HAs solution prepared by citric acid (1-3N) to produce matrix gel of Si-K-HAs. The Si-K-HAs matrix gel products are characterized by Fourier Transform InfraRed (FTIR), X-ray fluorescence (XRF), and Brunauer-Emmett-Teller (BET) analysis. The acidification process was carried out in neutral to acid (pH 3-7) conditions and the results showed that at neutral pH no Si-K-HAs gel formed. IR spectra confirmed the presence of humic acid in the gel product, whereas XRF analysis confirmed the presence of potassium (K) and silica (SiO<sub>2</sub>) in the gel product. The molar ratio of SiO<sub>2</sub>:K<sub>2</sub>O in the product is 0.9-0.3 in the pH range of 3-5. Si-K-HAs powder can be used as soil fertilizer especially for soils that lack silica, humic, and potassium nutrients or for future application development.

**Keywords:** geothermal sludge; gradual extraction; humic substance; matrix gel

**How to Cite This Article:** Muljani, S., Wahyudi, B., Suprihatin, and Sumada, K., (2018), Synthesis of Matrix Si-K-HAs Gel from Geothermal Sludge and Peat, Reaktor, 18(2), 76-83, <http://dx.doi.org/10.14710/reaktor.18.2.76-83>.

### INTRODUCTION

Indonesia has the largest area of peatlands in South East Asia, which are distributed in Sumatra, Kalimantan and Papua islands. However, the peat lands in Indonesia have been degraded rapidly by deforestation due to logging and agriculture,

construction of drainages and forest fires (Siegert *et al.*, 2011). Peat land degradation often occurs due to land use for agriculture, plantation or for industrial development. The process of converting peat lands generally begins with deforestation followed by the draining of peat land. Peat lands could not be recovered

so that water released from peat lands will lose their ability to store water. The peat lands that have lost water are prone to fire in the dry season and prone to flooding in the rainy season.

Humic acid (HA) is a major component of humic substance (HAs), which is the main organic constituent of soil (humus), peat and coal. It is produced by biodegradation of dead organic matter. It is not a single acid but rather a complex mixture of many different acids that contain carboxyl and phenolic groups so the mixture behaves functionally as a two-base acid or, sometimes, as an alkaline acid. (Saito and Seckler, 2014). The macromolecular structure of humic substances (HAs), i.e. molecular size, shape, conformation, and weight is believed to control key physico-chemical reactions in aquatic systems. However, these properties of HAs are still deeply a matter of debate (Baalousha *et al.*, 2006). On the other hands silica has become important globally because it produces resistance to many plants against disease and pests, and can contribute to the decline of pesticide and fungicide applications. Silica is also now considered an environmentally friendly element. This research is an effort to provide a fire suppression material in peat soil as well as provide nutrients and silica elements that are useful for plant growth.

Hybrid organic/inorganic materials derived through sol-gel processing have been extensively studied and reviewed. These hybrid materials combine the properties of inorganic and of organic compounds in one material (Sandor *et al.*, 2016). Several studies on the synthesis of alkali-silica-humic acid have been carried out but have not involved gelation method. Most products are obtained through the process of mixing some raw materials to produce a solid fertilizer (Roger *et al.*, 1971) or as support immobilization of humic acid to silica gel (Sandor *et al.*, 2016; Alexander *et al.*, 2016; Prasety *et al.*, 2016). The gelation is that cluster grow by condensation of polymer aggregation of particulate until the clusters collide, then links form between the clusters to produce a single giant cluster that is called a gel (Brinker, 1990; Muljani *et al.*, 2014). The present study developed a gelation process to form a combined gel matrix of silica, potassium, and HAs. To support nutrients in gel matrix, potassium hydroxide is used as a solvent to form potassium silicate. Potassium silicate with a standard of fertilizer is known to be quite effective (Buck *et al.*, 2008; Muljani *et al.*, 2016). On the other hands potassium humates derived from lignite (Zhang *et al.*, 2015) are alkaline, rich in carboxylic and phenolic groups, aromatic in nature provide favorable conditions for biological activity, chemical reactions and physical improvement of soil (Shujrah *et al.*, 2010).

Silica from geothermal sludge is amorphous structure (Muljani *et al.*, 2014) and is known that amorphous silica soluble in alkaline but insoluble at low pH (Iller, 1991). Meanwhile, HAs are materials that are insoluble under acidic conditions (at  $\text{pH} < 2$ ) but soluble at higher pH values, and humin is the humic substances fraction that is insoluble in water at any pH

(Stevenson, 1994). HAs extraction from some materials ie coal, soil, leaf and mine has been done using sodium hydroxide as solvent (Michael *et al.*, 2007; David *et al.*, 2014). HA can also be reduced from sodium-humic solutions by ion-exchange methods (Kurniati *et al.*, 2018). Each of the HAs from these ingredients has slightly different IR spectra characteristics (Yamaguchi *et al.*, 1998).

Based on the same solubility properties, HAs and silica allow to be extracted gradually or simultaneously. In gradual extraction, two extraction steps are carried out as follows: 1) extraction of HAs from peat using potassium hydroxide to obtain potassium-humic solution, 2) potassium-humic solution used to extract silica from geothermal mud. While for the extraction simultaneously is done by mixing peat and sludge materials and then extracting the mixture of both materials using alkaline hydroxide solution. No previous research information was found on peat and silica extraction either gradually or simultaneously.

The formation of hydrogel silica from sodium silicate by acidification and polymerization reaction is influenced by several factors such as silica concentration, pH, aging time, and acid concentration (Muljani *et al.*, 2014; Kalapathy *et al.*, 2002; Brinker, 1990). This research involves HAs in polymerization reaction to form silica-humic hydrogel. Types of acids ie organic acids or inorganic acids used as catalysts for hydrogel formation are generally less influential. Citric acid is generally used as a buffer solution to control the pH of the solution. Kalapathy *et al.* (2002) reported the preparation of silica gels by an improved method using citric acid and oxalate to control the pH of the solution. Citrate ions can react with many metal ions to form citrate salts. The acidity of citric acid is obtained from three hydroxyl groups which can release protons in solution. Elizabeth *et al.* (2010) reported that the precipitation of silica will occur in very acidic conditions. The form of the silica monomer in the solution is immediately polymerized to form the primary particles and subsequently flocculates. The acid-catalyzed mechanisms are preceded by protonation of OH or OR substituents attached to silica (Brinker, 1988). The gel is fragmented and the flocs densify until a suspension is obtained. Control of size and structure of the resulting aggregates were strongly influencing product properties (Quarzh *et al.*, 2010). Polymerization occurs when the concentration of silica exceeds 140 mg/l, but this can be prevented by the presence of humic acid. Humic substances and other organic acids are known to form complexes or chelates with silica (Tan, 2010). The present study was intended to form a gel matrix of a silica-potassium-humic substance (Si-K-HAs) by controlling the concentration of citric acid and pH value in the acidification and polymerization process. The acidification process in this study is carried out in neutral to acidic conditions because it is reported that the appearances of humic acid is generally at low pH (Baalousha *et al.*, 2006; Kurniati *et al.*, 2018).



## MATERIALS AND METHODS

### Sample Preparation

Geothermal sludge as a source of silica obtained from Dieng East Java, while peat as a source of HA obtain from Banjarmasin. Both raw materials are crushed to pass through a 100-mesh sieve. Potassium hydroxide (95.5%) as solvent and citric acid (high purity) for acidification process was obtained from chemical distributor CV Medica, Surabaya both in solid form. Subsequently the potassium hydroxide solution and citric acid solution were prepared by dissolution and dilution process using demineralized water. Provides a 2 N potassium hydroxide (KOH) solution and a citric acid solution of 1; 1.5; 2; 2.5; 3 N. To find out the presence of humic acid (HA) in peat is also carried out peat (15 grams) extraction using 300 ml KOH 2 N solution and acidification using citric acid (2 N) until it reaches pH 2 to form HA solids. The HA solid is then observed its morphology using SEM images.

### Gradual Extraction and Acidification

Peat of 15 grams extracted using 300 ml KOH 2 N solution in an Erlenmeyer flask conducted with constant stirring using a magnetic stirrer to dissolve humic substances and produce a potassium humate (K-HAs) solution. The solution was then filtered through Whatman No. 41 ashless filter paper. The K-HAs solution subsequently used as a solvent for the extraction of silica from geothermal sludge (10 grams) at 100°C for 1.5 hours accompanied by stirring using a hot plate stirrer. The extraction of silica by K-HAs solution produces a filtrate of silica potassium humic substances (Si-K-HAs). The extraction of silica using K-HAs solution was produced filtrate silica potassium humic (Si-K-HAs) by filtration using Whatman No. 41 ashless filter paper.

The Si-K-HAs solution obtained as described above was used to produce Si-K-HAs gels. The solution was then titrated with citric acid under constant stirring and constant flow rate (0.7 ml/min) using syringe pump. 15 ml of the Si-K-HAs solution sample was titrated using citric acid at various concentration i.e. 1; 1.5; 2; 2.5; and 3 N until the pre-specified pH was reached i.e. 3; 4; 5; 6; and pH 7. After acidification, the solution is allowed for aging to form a solid gel for 48 h. The gel is then dried in the oven for 24 h at 100°C. The dried gel was subsequently crushed to obtain a powder of about 100 mesh. The experimental procedure for preparation Si-K-HAs matrix gel by gradual extraction and acidification methods presented as a stepwise schematic in Figure 1.

### Characterization

The composition of geothermal sludge and Si-K-HAs powder was analysed by X-ray fluorescence (XRF, Minipal 4, PANalytical). Functional group on products Si-K-HAs characterized by Fourier Transform Infrared (FTIR). The measurement were made with a Perkin Elmer spectrometer in the range of 400-3000  $\text{cm}^{-1}$ . Nova 1200 gas sorption analyzer instrument used

to characterized the nitrogen adsorption-desorption isotherms of the Si-K-HAs gels at 77 K. The surface area determined from the adsorption-desorption isotherms by Brunauer-Emmet-Teller (BET) method while pore size, pore volume and pore distribution determined by desorption branch using Narret-Joyner-Halenda (BJH) method. Scanning Electron Microscopy (SEM) was used to observe the morphology of the samples.

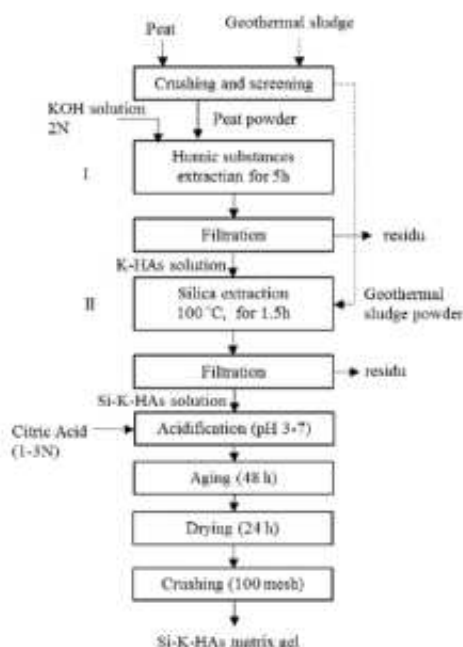


Figure 1. Schematic of experimental procedure for the preparation of Si-K-HAs matrix Gel

## RESULTS AND DISCUSSION

### Extraction of Silica and Humic Substance

The silica content of geothermal sludge characterized using XRF, was about 93 wt%. The extraction of peats using KOH 2 N solution yielded a K-HAs solution with a measured pH of about 13.3 using pH meters. The resulting filtrate is then used for the extraction of silica from geothermal sludge to produce Si-K-HAs solution. The results showed no residual solids in the silica extraction process indicated that all the silica (10 g) dissolved in the K-HAs as solvents (about 300 ml). The concentration of silica in Si-K-HAs solution is about 2.86 %w.

Figure 2 showed IR spectra on Si-K-HAs solution and K-HAs solution prepared by KOH 2 N solution. Wang *et al.* (2017) reported that the FTIR spectrum of coal and its derivatives can be divided into four regions: 900-700  $\text{cm}^{-1}$  (aromatic substitution), 1800-1000  $\text{cm}^{-1}$  (O-containing groups), 3000-2800  $\text{cm}^{-1}$  (aliphatic structure), and 3700-3000  $\text{cm}^{-1}$  (hydrogen bond regions). Inorganic silicates and

clay type materials have very characteristic spectra. There is a characteristic strong band centered around  $1100\text{ cm}^{-1}$  which sometimes appears as one band and in other samples as multiple bands. There may also be bands due to associated water molecules around  $3400\text{ cm}^{-1}$  and  $1640\text{ cm}^{-1}$ . The absorption band centered at  $1720\text{ cm}^{-1}$  (indicating acidic carboxyl groups) was clearly stronger for HAs from peat with higher degree of decomposition. As shown in Figure 2 the difference IR spectra K-HAs solution from the first extraction stage and the Si-K-HAs solution from the second extraction stage is the appearance of absorption at the wavenumber  $1100\text{ cm}^{-1}$  indicating the vibration of siloxane (Si-O-Si).

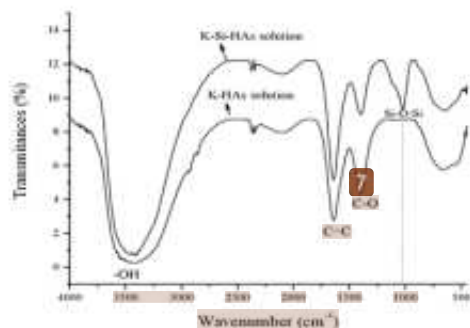


Figure 2. IR spectra of K-HAs solution and Si-K-HAs solution prepared by KOH solution.

**Effect of Citric Acid Concentration**

The Si-K-HAs solution produced from extraction process is then acidified with citric acid (1-3 N) to reach a pH that is adjusted in the range of 3 to pH 7. The presence of humic substances has no significant effect on the gel formation of Si-K-HAs during the polymerization process (aging). However, gel formation with the presence of humic substances is relatively longer than gel formation without the presence of humic substances as reported in previous studies (Muljani, 2014). The Si-K-HAs gel product is dark brown similar to humic acid color, but after the gel is dried ( $100^{\circ}\text{C}$ ) the brown color is uneven.

Figure 3 showed the IR spectra Si-K-HAs product in various citric concentrations. IR spectra were similar to each other in terms of the primary position of adsorption, but differences of various entities were apparent in the relative intensity of some bands, depending on acid concentrations.

To identify the presence of salt groups formed by the presence of potassium and citric acid can be explained as the following description. Carboxylic acid salts typically show a strong, characteristic asymmetric stretching absorption from the  $\text{COO}^-$  group in the  $1650\text{--}1550\text{ cm}^{-1}$  region. The corresponding symmetric stretching absorption occurs at around  $1440\text{--}1335\text{ cm}^{-1}$ . For acid salts with a strongly electronegative group the asymmetric stretching absorption will shift to higher frequencies (around  $1690\text{ cm}^{-1}$ ). Fairly strong rocking

in and out of plane deformation absorptions are observed in the  $770\text{--}400\text{ cm}^{-1}$  region.

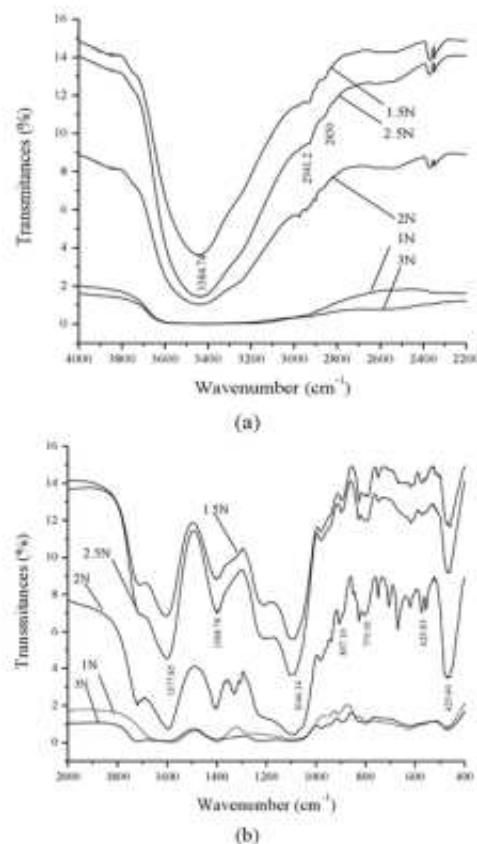


Figure 3. IR spectra Si-K-HAs gel on various concentration of citric acid at wavenumber a)  $4000\text{--}2000\text{ cm}^{-1}$ , and b)  $2000\text{--}450\text{ cm}^{-1}$

The carboxylic acids are tremendously more acidic than the very weak organic acids (alcohols). As a result, the aliphatic carboxylic acids readily form the carboxylate ion in aqueous solutions. A water soluble organic compound that dissolves in cold, dilute aqueous potassium hydroxide is almost always a carboxylic acid. When ionization of the acid occur giving rise to the  $\text{R-COO}^-$  group, resonance is possible between the two  $\text{-CO}^-$  groups. As a result, the characteristic acid group absorption around  $1700\text{ cm}^{-1}$  disappears and is replaced by two bands; the first occurs between  $1615\text{--}1550\text{ cm}^{-1}$  and the second in the  $1400\text{--}1300\text{ cm}^{-1}$  region. These absorptions correspond to the asymmetric and symmetric vibrations of the  $\text{R-COO}^-$  group. Of these two bands, the band around  $1600\text{ cm}^{-1}$  is most indicative since the symmetric absorption occurs in the crowded fingerprint region.

As shown on Figure 3a the strong absorption peak at the wavenumber  $3384\text{ cm}^{-1}$  shows the vibration of the  $\text{-OH}$  indicates the bands due to associated water



molecules. The absorption at wavelengths of  $2941.2\text{ cm}^{-1}$  and  $2850\text{ cm}^{-1}$  identified the weak absorption due to the vibration of  $\text{CH}_3$ - and  $\text{CH}_2$ - group, respectively. Figure 3b showed the split of IR spectra in the range of  $2000$  to  $450\text{ cm}^{-1}$  wavenumber. The adsorption band around  $1620\text{ cm}^{-1}$  is indicated of the existence of carboxylate group with stretching of CH bonds observed around  $2940\text{ cm}^{-1}$ , also indicated of interaction between silica and these groups. The absorption band at wavenumber  $1637.43\text{ cm}^{-1}$  is interpreted as  $-\text{C}-\text{C}-$  which hydrogen bonds. The presence of a C-O vibration from  $-\text{COOH}$  is identified by the appearance of absorption at wave number  $1261.12\text{ cm}^{-1}$ . Humic acid has a characteristic that is the appearance of spectra at wavenumber around  $950$ - $1000\text{ cm}^{-1}$ . All results presented above were obtained for silica gels produced at a gelation pH of 4.

Figure 4 showed SEM images for Si-K-HAs gel prepared by citric acid  $2.5\text{ N}$  (pH 4) and typical morphology of HA solid prepared by  $\text{KOH } 2\text{ N}$ . It appears that the Si-K-HAs gel particles are more dense than the humic acid particles, indicating that the humic substance is involved in forming the matrix with silica during the gelation process.

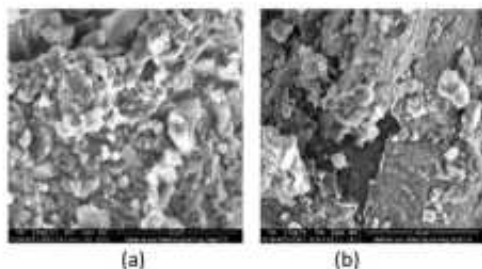


Figure 4. A typical morphology of a) the Si-K-HAs gel prepared by citric acid and b) HA solid prepared by  $\text{KOH } 2\text{ N}$

#### Effect of Gelation pH

As previously described, the acidification of the Si-K-HAs solution with citric acid is carried out until it reaches the adjusted pH. Furthermore, to investigate the effect of gelation pH,  $2.5\text{ N}$  citric acid was used for the acidification process. The results showed that the gelation time was different for each gelation pH. The higher of the gelation pH, the faster gelation time ie from  $20\text{ h}$  (pH 3) to about  $30\text{ min}$  (pH 5). Typically polymerization for the pH gelation 7 particles rapidly forms aggregate or flocculates very rapidly (Iler, 1978; Brinker, 1990; Muljani *et al.*, 2014), but the result showed that flocculation has not yet occurred until reach  $60\text{ h}$  gelation time. The observations at pH 6 showed that aging for  $60\text{ h}$  the solution formed a fragile and weak solid wherein some solutions remained liquid. While at pH 7 the gel has not formed until it reaches  $60\text{ h}$  aging time. The observation at this pH refers to the amount of citric acid added insufficient so that the salt formed is also small where this causes the low viscosity of the solution.

Figure 5 showed the IR spectra of Si-K-HAs product prepared by citric acid at pH 3 to 6. As shown in Figure 5a the absorption at wavenumbers  $3346.50\text{ cm}^{-1}$  and  $3388.50\text{ cm}^{-1}$  indicated the presence of O-H vibration. The weak absorption at wavenumber  $2365.60\text{ cm}^{-1}$  shows  $-\text{OH}$  vibration, while absorption at wavenumber  $1637.55\text{ cm}^{-1}$  shows vibration  $\text{C}-\text{O}$  as shown in Figure 5b. IR spectra were similar to each other in terms of the primary position of adsorption, but differences of various entities were apparent in the relative intensity of some bands, depending on pH value. At  $\text{pH} > 5$  there is almost no visible absorption, this indicates a gel matrix formed predominantly of potassium.

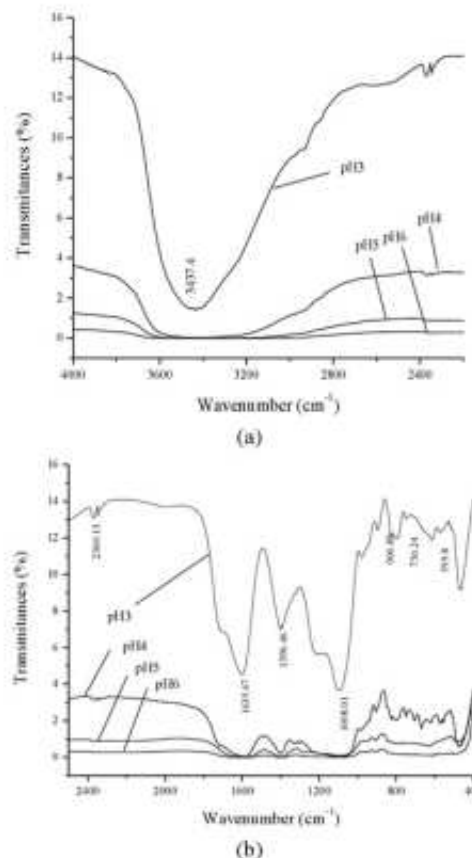


Figure 5. IR spectra Si-K-HAs gel on various pH value at wavenumber a)  $4000$ - $2200\text{ cm}^{-1}$ , and b)  $2500$ - $450\text{ cm}^{-1}$ .

Table 1 corresponds to Figure 6 shows some of the components contained in the Si-K-HA (matrix gel) product. An increase in pH value from pH 3 to 5 causes an increase in  $\text{K}_2\text{O}$  concentration from  $49$  to about  $72\%$  but instead decreases  $\text{SiO}_2$  concentration from  $47$  to  $25\%$ . The result is that the  $\text{SiO}_2:\text{K}_2\text{O}$  molar ratio in the gel matrix product decreases from about  $0.95$  to  $0.35$  as the pH increases from  $3$  to  $5$ . The level of acidity or pH

value adjusted in the acidification process indicates a significant effect on the characteristics of Si-K-HAs products.

Table 1. SiO<sub>2</sub>:K<sub>2</sub>O molar ratio in matrix gel product

pH	SiO <sub>2</sub> (%)	K <sub>2</sub> O (%)	SiO <sub>2</sub> :K <sub>2</sub> O
3	47.1	49.3	0.95
4	37.5	59.2	0.63
5	25.1	71.9	0.35

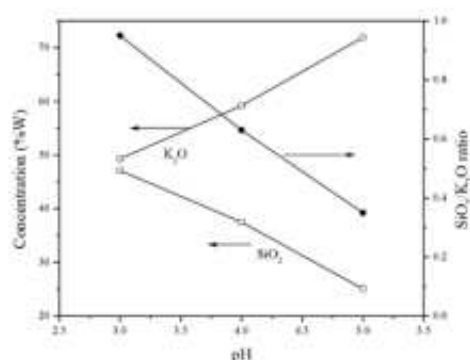


Figure 6. Effect of pH on SiO<sub>2</sub> and K<sub>2</sub>O composition in Si-K-HAs gel prepared by citric acid

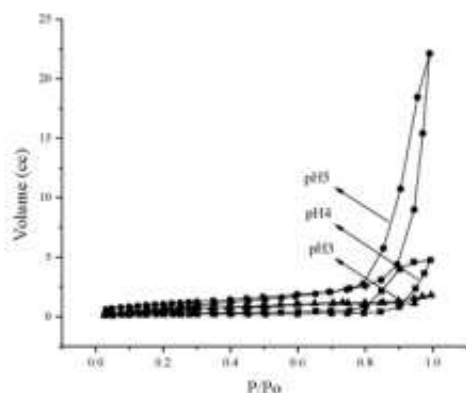


Figure 7. Adsorption-desorption isotherms of Si-K-HAs gels prepared by citric acid.

Figure 7 showed the typical adsorption-desorption isotherms Si-K-HAs matrix gel prepared from geothermal sludge and peat using citric acid for acidification at adjusted pH 3, 4 and 5. The isotherms were typical type V according to the IUPAC classification which has a convex shape to relative pressure and is characteristic of the weak interaction between adsorbate and adsorbent. This isotherm type indicates indefinite multilayer formation after the completion of the monolayer. Moreover, the hysteresis can be classified as a type H3 hysteresis, in which aggregates (loose assemblages) of plate-like particles forming slit-like pores. This type of isotherm occurs in solids with a pore size of micropore or mesopore.

Table 2 showed the BET analysis of Si-K-HAs prepared by citric acid 2.5 N. The higher surface area at pH 4 of 24.470 m<sup>2</sup>g<sup>-1</sup> followed by pH 3 of 18.22 m<sup>2</sup>g<sup>-1</sup> and pH 5 of 16.494 m<sup>2</sup>g<sup>-1</sup>. The pH affects the polymerization process in which the monomers will form the polymer and the particle size continues to grow until they form a gel. While the pore size may be more influenced by the degree of compaction than the diameter of the primary particles.

Table 2. BET analysis Si-K-HAs gel product

pH	Surface area m <sup>2</sup> g <sup>-1</sup>	Pore volume cc g <sup>-1</sup>	Pore diameter nm
3	18.22	0.039	3.372
4	24.47	0.097	10.223
5	16.50	0.098	11.452

Figure 8 showed the pore distribution of Si-K-HAs prepared by citric acid. The distribution curve at pH 4 appears to have a narrow peak in the range of 12.32 - 30.22 nm indicating the pores in the mesopore region. The pore distribution at pH 5 is quite wide where most of it is in the mesopore region (2-50 nm) and partly in the macropore region (> 50 nm) which means less uniform pores. The pore distribution at pH 3 appears to be partially in the micropore region (< 2 nm) and partly mesoporous but the adsorption capacity is very low. It can be explained that at pH 3 the content of humic acid and high silica will make the pore diameter smaller but at pH 5 potassium begin to increase with decreasing silica content.

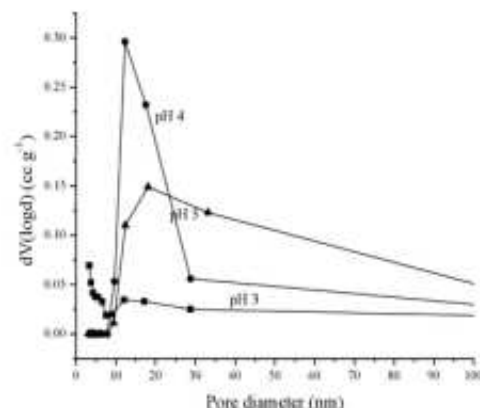


Figure 8. Pore distributions of Si-K-HAs gel prepared by citric acid.

The acid concentration and final pH value in the acidification process as described previously affects the product composition and its characteristics. The results showed that the ratio of silica: potassium was still relatively low (0.3-0.9) when compared to the ratio for commercial fertilizer (1.6-3.2). To be able to get a larger SiO<sub>2</sub>:K<sub>2</sub>O ratio then it is necessary to increase the concentration of silica.



## CONCLUSIONS

Matrix silica potassium humate (Si-K-HAs) gel has been successfully prepared from peat and geothermal sludge by a gradual extraction and acidification method. The Si-K-HAs gel can be formed through polymerization process following the gelation of silica. The presence of humic acid was relative no effected the formation of the gel and also coalesce with the silica. Nevertheless, there is still a need to further study the influence of humic on the polymerization of silica especially on various concentrations of silica.

The results of IR spectra and BET analysis show that the gel formed contains potassium, silica, humic acid and citrate. Gel product composition through XRF analysis obtained SiO<sub>2</sub>:K<sub>2</sub>O ratio between 0.3-0.9. The gel composition can be altered to increase the SiO<sub>2</sub>:K<sub>2</sub>O ratio by adjusting the ratio of raw materials and the volume or concentration of potassium hydroxide solvent. In addition, pH value and acid concentration as a controller in the gelation process also become a consideration to obtain the appropriate product characteristics.

The Si-K-HAs gel product has the high oxygen content of the functional group including carboxyl, hydroxyl, phenol, potassium, and silica and is widely recognized as an important natural material.

## ACKNOWLEDGEMENTS

We wis 25 thanks the Ministry of Research and Technology, Indonesia, for its financial support through Hibah Terapan Unggulan Perguruan Tinggi. We also thank PT Geodipa Energi for providing the geothermal sludge and Kadek Palgunadi for providing peats from Banjarmasin. Thanks to Ivan Atmanegara and Mardining Setyowati for assisting with the experiments.

## REFERENCES

31 Alexander, B.V., Sergey, A.P., Andrey, I.K., Hatfied, K., and Perminova, I.V., (2016). Nature-like Solution for Removal of Direct Brown 1 Azo Dye from Aqueous Phase Using Humics-Modified Silica Gel, *Chemosphere*, 145, pp. 83-88.

Baalousha, M., Mikael, M.H., and Le Coustumer, P., (2006). Conformation and Size of Humic Substances: Effects of Major Cation Concentration and Type, pH, Salinity, and Residence Time, *Colloid and Surface a Physicochemical and Engineering Aspect*, 272 (1-2), pp. 48-55.

Brinker, C.J. and Scherer, G.W., (1990). *Sol-Gel Science: The Physics and Chemistry of Sol-Gel Processing*. Academic Press: San Diego, CA, USA.

Brinker, C.J., (1988). Hydrolysis and Condensation of Silicates: Effects on Structure, *Journal of Non-Crystalline Solids*, 100, pp. 31-50.

6 Buck, G.B., Gaspar, H.K., Nolla, A., and Coelho, L., (2008). Potassium Silicate as Foliar Spray and Rice Blast Control, *Journal of Plant Nutrition*, 31, pp. 231-237

Elizabeth, A.C. 14 Pattanapong, W., Sasanka, R., and Scott, F.H., (2010) Silica Precipitation in Acidic Solutions: Mechanism, pH Effect, and Salt Effect, *Langmuir*, 26 (13), pp. 10467-10474

8 Iler, R.K., (1978). *The Chemistry of Silica-Solubility, Polymerization, Colloid and Surface Properties, and Biochemistry*. John Wiley & Sons: New York, NY, USA.

10 Kalapathy, A., Proctor, A., and Shultz, J., (2002). An Improved Method for Production of Silica from Rice Hull Ash, *Bioresource Technology*, 85, pp.285-289.

Kurniati, E., Muljani, S., Virgani, D.G., and Neno, B.P., (2018). Humic Acid Isolations from Lignite by Ion Exchange Method, *Journal of Physics: Conference Series*, 953 (1), 012234.

Michael, T., Stemmer, M., Spiegel, H., Christian, K., Harberhauer, G., Mentler, A., and Martin, H., (2007). FTIR-spectroscopic Characterization of Humic Acids and Humin Fractions Obtained by Advanced NaOH, Na<sub>4</sub>P<sub>2</sub>O<sub>7</sub>, and Na<sub>2</sub>CO<sub>3</sub> Extraction Procedures, *Journal of Plant Nutrition and Soil Science*, 170 (4), pp. 522-529.

Muljani, S., Wahyudi, B., Sumada, K., and Suprihatin., (2016). Potasium Silicate Foliar Fertilizer Grade from Geothermal Sludge and Pyrophyllite, *MATEC Web of Conferences*, 58, Les Ulis: EDP Sciences.

Muljani, S., Setyawan, H., Wibawa, G., and Altway, A., (2014). A Facile Method for the Production of High-Surface-Area Mesoporous Silica Gels from Geothermal Sludge, *Advanced Powder Technology*, 25 (5), pp. 1593-1599

Prasety, E. and Toyoda, K., (2016). Sol-gel Synthesis of a Humic Acid-Silica Gel Composite Material as Low-Cost Adsorbent for Thorium and Uranium Removal, *Journal of Radioanalytical and Nuclear Chemistry*, 310, pp. 69-80.

Roger, W.M., (1971). Alkalated Humic Acid-Silica Compositions for Fertilizers and the Like and Methods of Making Same, *US 3552943A*.

Sandor, M., Nistor, C.L., Szalontai, G., Stoica, R., Nicolae, C.A., Elvira, A., Fazakas, J., Oancea, F., and Donescu, D., (2016). Aminopropyl-Silica Hybrid Particles as Supports for Humic Acids Immobilization, *Materials*, 9(34), p. 34.

Saito, B. and Seckler, M.M., (2014). Alkaline Extraction of Humic Substances from Peat Applied to

Organic-Mineral Fertilizer Production, *Brazilian Journal of Chemical Engineering*, 31(3), pp. 675 – 682

Sjogert, F., Boehm, H.D.V., Rieley, J.O., Page, S.E., Jauhainen, J., Vasander, H., and Jaya, A., (2001), Peat fires in Central Kalimantan, Indonesia: Fire impacts and carbon release. *Proceeding of International Symposium on Tropical Peatland*, Singapore, p. 99

Shujrah, A.A., Khanif, Y.M., Hussin, A., Othman, R., and Ahmed, O.H., (2010), Impact of Potassium Humate on Selected Chemical Properties of an Acidic Soil, *Proceedings of the 19<sup>th</sup> World Congress of Soil Science*, pp.119-122.

Stevenson F.J. (1994) *Humus Chemistry: Genesis, Composition, Reactions*. 2<sup>nd</sup> ed. N.Y.: Wiley.

Tan, K.H., (2008), *Soils in the Humid Tropics and Monsoon Region of Indonesia*, 1<sup>st</sup> ed, CRC Press: Taylor & Francis Group, pp. 103-104

Wang, C.F., Fan, X., Zhang, F., Wang, S.Z., Zhao, Y.P., Zhao, X.Y., Zhao, W., Zhu, T.G., Luc, J.L., and Wei, X.Y., (2017), Characterization of Humic Acids Extracted from a Lignite and Interpretation for the Mass Spectra, *Royal Society of Chemistry Advances*, 7, 20677

Yamaguchi, T., Hayashi, H., Yazawa Y., Uomori, M., Yazaki, F., and Bambalov, N.N., (1998), Comparison of Basic Characteristics of Humic Acids Extracted from Peats and Other Sources, *International Peat Journal*, 8, pp. 87-94.

Zhang, P., Yao, C., and Hongwen, M., (2015), Method for Producing Potassium Humate Employing Potassium-Rich Rock and Lignite, *CN10460909A*.

# 13 Synthesis of Matrix Si-K-HAs Gel from Geothermal Sludge and Peat

ORIGINALITY REPORT

# 11%

SIMILARITY INDEX

PRIMARY SOURCES

- 1** Abdullah Al Mamun, Mohammed A. AlSaadi, Md. Zahangir Alam, Iis Sopyan. "Carbon nanotubes grown on oil palm shell powdered activated carbon as less hazardous and cheap substrate", *Applied Nanoscience*, 2018  
Crossref 111 words — 2%
- 2** Syawal, Yustiwati. "Effect of peat fire on chemical characteristics of humic acid and fulvic acid in soil and water of peatland of Central Kalimantan, Indonesia [an abstract of dissertation and a summary of dissertation review]", *Hokkaido University Collection of Scholarly and Academic Papers*, 2014.  
Publications 41 words — 1%
- 3** Mika Vähä-Nissi, Marja Pitkänen, Erkki Salo, Eija Kenttä et al. "Antibacterial and barrier properties of oriented polymer films with ZnO thin films applied with atomic layer deposition at low temperatures", *Thin Solid Films*, 2014  
Crossref 33 words — 1%
- 4** [mgumus.chem.msu.ru](http://mgumus.chem.msu.ru)  
Internet 25 words — < 1%
- 5** [archive.org](http://archive.org)  
Internet 25 words — < 1%
- 6** [www.avocadosource.com](http://www.avocadosource.com)  
Internet 24 words — < 1%
- 7** [repository.ntu.edu.sg](http://repository.ntu.edu.sg)  
Internet 23 words — < 1%



8	<a href="https://res.mdpi.com">res.mdpi.com</a> Internet	22 words — < 1%
9	K. Quarch, E. Durand, C. Schilde, A. Kwade, M. Kind. "Mechanical fragmentation of precipitated silica aggregates", <i>Chemical Engineering Research and Design</i> , 2010 Crossref	22 words — < 1%
10	<a href="https://fedetd.mis.nsysu.edu.tw">fedetd.mis.nsysu.edu.tw</a> Internet	21 words — < 1%
11	"Effect of Temperature in Extraction of High Purity Amorphous Silica from Rice Husk for Silicon Production", <i>EPD Congress 2015</i> , 2015. Crossref	19 words — < 1%
12	<a href="http://www.bioag.com">www.bioag.com</a> Internet	18 words — < 1%
13	Shilin Liu, Jinping Zhou, Lina Zhang. " Effects of Crystalline Phase and Particle Size on the Properties of Plate-Like Fe O Nanoparticles during $\gamma$ - to $\alpha$ -Phase Transformation ", <i>The Journal of Physical Chemistry C</i> , 2011 Crossref	16 words — < 1%
14	<a href="https://repositories.lib.utexas.edu">repositories.lib.utexas.edu</a> Internet	15 words — < 1%
15	Stephanie Evers, Catherine M. Yule, Rory Padfield, Patrick O'Reilly, Helena Varkkey. "Keep wetlands wet: the myth of sustainable development of tropical peatlands - implications for policies and management", <i>Global Change Biology</i> , 2017 Crossref	14 words — < 1%
16	<a href="https://zenodo.org">zenodo.org</a> Internet	14 words — < 1%
17	D F Rosida, Happyanto, Anggraeni, Sugiarto, Hapsari. " Technology Development of Salak ( ) Chips With Vacuum Frying Machine Base On Expert System In	14 words — < 1%

- 
- 18 Busuioc, A.M.. "Structural features and photocatalytic behaviour of titania deposited within the pores of SBA-15", Applied Catalysis A, General, 20060908  
13 words — < 1%  
Crossref
- 
- 19 china.iopscience.iop.org  
13 words — < 1%  
Internet
- 
- 20 www.electrochemsci.org  
12 words — < 1%  
Internet
- 
- 21 physchemres.org  
12 words — < 1%  
Internet
- 
- 22 Carlsson, D. O., J. Lindh, L. Nyholm, M. Strømme, and A. Mihranyan. "Cooxidant-free TEMPO-mediated oxidation of highly crystalline nanocellulose in water", RSC Advances, 2014.  
11 words — < 1%  
Crossref
- 
- 23 Kim, M.. "Comparison of the adsorbent performance between rice hull ash and rice hull silica gel according to their structural differences", LWT - Food Science and Technology, 200805  
11 words — < 1%  
Crossref
- 
- 24 Marta Elena Díaz-García. "Molecular Imprinting in Sol-Gel Materials: Recent Developments and Applications", Microchimica Acta, 02/2005  
11 words — < 1%  
Crossref
- 
- 25 Aji Prasetyaningrum, Bakti Jos, Yudhy Dharmawan, Ratih V. Octaviani, Ratnawati Ratnawati. "Chemical and Spectral Characterization of The Ozonation Products of  $\kappa$ -Carrageenan", MATEC Web of Conferences, 2018  
10 words — < 1%  
Crossref

---

26 R STEPHENS, E BRADBURY. "Interaction between carboxylic acids and the peptide group", Polymer, 1976 10 words — < 1%  
Crossref

---

27 usir.salford.ac.uk 9 words — < 1%  
Internet

---

28 Sadaf, Sana, Haq Nawaz Bhatti, Shaukat Ali, and Khalil-ur Rehman. "Removal of Indosol Turquoise FBL dye from aqueous solution by bagasse, a low cost agricultural waste: batch and column study", Desalination and Water Treatment, 2014. 9 words — < 1%  
Crossref

---

29 Ewa Lipczynska-Kochany. "Effect of climate change on humic substances and associated impacts on the quality of surface water and groundwater: A review", Science of The Total Environment, 2018 9 words — < 1%  
Crossref

---

30 Q.-H. Xia. "Structure, Acidity, and Catalytic Activity of Mesoporous Acid Catalysts for the Gas-Phase Synthesis of MTBE from MeOH and ButOH", Journal of Catalysis, 20020725 8 words — < 1%  
Crossref

---

31 Natalia S. Shcherbina, Stepan S. Kalmykov, Leonid A. Karpiouk, Sergey A. Ponomarenko et al. "Nonreversible Immobilization of Water-Borne Plutonium onto Self-Assembled Adlayers of Silanized Humic Materials", Environmental Science & Technology, 2014 6 words — < 1%  
Crossref